

Water drainage and gas collection with geocomposites - Hydraulic software



Stephan Fourmont
Afitex-Textel, Ste Marie, Quebec, Canada
David Beaumier, Justine Decaens
CTT Group Sageos, St Hyacinthe, Quebec, Canada

ABSTRACT

Geosynthetic materials and, more specifically, drainage geocomposites are now widely used for water drainage and gas collection in applications as varied as final landfill covers, leachate collection in landfill cells, sub-slab depressurization systems under buildings, groundwater drainage under embankments, etc. The design methods used are based on the in-plane flow capacity of the geocomposites, which is determined by laboratory tests performed on 250-300 mm long product specimens. Fluid is injected into the thickness of the product and the drainage capacity is interpolated for an actual length of several meters. This paper presents the development of a hydraulic design software for geocomposites and granular drainage layers, based on soil hydraulic and flow capacity characterization of geocomposites through laboratory tests. The software provides a model of the hydraulic curves in the geocomposites depending on the application for which the geocomposites are used, and the fluid to be drained (water, landfill gas, methane, air, etc.).

RÉSUMÉ

Les matériaux géosynthétiques et plus particulièrement les géocomposites de drainage sont aujourd'hui largement utilisés pour le drainage des eaux et la collecte des gaz dans des applications aussi variées que les couvertures finales de Lieux d'Enfouissement Technique (LET), la collecte des lixiviats dans les cellules de déchets, les systèmes de dépressurisation sous les bâtiments, le drainage des eaux souterraines sous les remblais, etc. Les méthodes de dimensionnement sont basées sur la capacité de débit dans le plan des géocomposites, qui est déterminée par des essais en laboratoire réalisés sur des échantillons de produit de 250 à 300 mm de long. Un fluide est injecté dans l'épaisseur du produit et sa capacité de drainage est interpolée pour une longueur réelle de plusieurs mètres. Cet article présente le développement d'un logiciel de dimensionnement hydraulique pour les géocomposites et les couches drainantes en matériaux granulaires, basé sur les caractéristiques hydrauliques des sols et sur la capacité de drainage des géocomposites. Le logiciel permet de caractériser la répartition des charges hydrauliques dans les géocomposites en fonction du type d'application et du fluide à drainer (eau, gaz de décharge, méthane, air, etc.).

1 INTRODUCTION

The design of geosynthetic materials for drainage requires an excellent knowledge of the material's hydraulic properties. The determination of the drainage capacity of drainage geocomposites is based on in-plane flow as determined by laboratory tests according to ASTM D4716, GRI GC15, and ISO 12958-2. The initial type tests allow the designer to correlate the flow rate with the hydraulic head or hydraulic gradient.

In addition to the basic hydraulic characterization, the long-term in-situ drainage capacity of the geocomposite is calculated from these laboratory test results using guidance documents that help the designer address the reduction factors to be applied to the drainage flow capacity as a function of the type of geocomposite, the engineered structure, type of fluid (water, gas), etc.

The ASTM D7931 standard guide (based on ASTM D4716 laboratory test), or the ISO/TR 18228-4 standard guide (based on ISO 12958 laboratory test) greatly help the engineers in this regard, but certain points can be misleading for engineers without solid expertise in geosynthetics.

1.1 Laboratory tests

The in-plane flow capacity (or Transmissivity) of geocomposites is developed to be compatible with the whole range of products on the market through ASTM and ISO standards. Because of the different physical characteristics of drainage geocomposites, the laboratory tests performed as per the standards may not be as accurate as expected.

For example, the testing device typically used has a length of 250 mm to 300 mm, underestimating by at least 30% the drainage capacity of DRAINTUBE multi-linear drainage geocomposites (Blond et al., 2013). This is because the entrance and exit transition flow to the tested length causes additional head losses.

Moreover, taking a single test measurement (even after a seating time of several hours), may not account for the continuous compression of the tested product due to creep throughout its service life and lead to an overestimation of its in-situ drainage capacity. This is particularly noticeable for geocomposites with a monofilament core where the in-situ drainage capacity can be more than 10 times lower than the value measured in the laboratory test (Zanzinger, 2000).

1.2 Boundary conditions

The drainage capacity of the geocomposite is determined by using laboratory tests with specific test conditions, such as hydraulic gradient, vertical compression load, seating time, and material(s) in contact with the geocomposite. It can be complicated for the designer to correlate these test conditions with the field conditions, or even more concerning, to be aware that the test conditions have a significant impact on the given results.

For example, using steel plates as boundary conditions when testing a drainage geocomposite does not address the geotextile intrusion into the drainage core. This phenomenon will occur in the field when the product is in contact with a soil layer. This typically leads to a significant reduction in flow rate for most drainage geocomposites, up to 90% reduction for geocomposites under high compressive loads (Zhao et al., 1999).

As for creep in compression, the sensitivity to the boundary conditions depends on the type and structure of the drainage geocomposite.

1.3 Terminology

The technical terms involved in hydraulic design can be a source of confusion for the designer. Indeed, depending on their field of expertise, geotechnical or geosynthetic, some identical terms do not represent the same quantities and are not directly comparable. One example is "Hydraulic Transmissivity". It is not directly comparable between a granular layer and a geocomposite. The first one is an intrinsic value of a given granular layer, while the second one depends on many factors specific to the geocomposite environment such as the hydraulic gradient, the applied normal load, the material in contact, etc.

2 SOFTWARE DEVELOPMENT

In the trend of Computer Assisted Design (CAD) for engineers, Afitex Group has developed a software for the design of geosynthetics used in drainage applications. The new software, named Lympha, assists designers in the hydraulic selection of drainage geocomposites (including multi-linear drainage geocomposites) as well as granular drainage layers using site-specific conditions.

The software is based on a previous model developed with LIRIGM university research laboratory at the University of Grenoble (France) and CEREMA (formerly Laboratoire Régional des Ponts et Chaussées de Nancy). It has been updated and improved with the contribution of the SAGEOS (CTT Group, Quebec), the CEGEP of Saint-Hyacinthe (Quebec), and the University of Saskatchewan.

2.1 Project presentation

The development of the software has been divided into the following three main steps:

- The Calculation core for multi-linear drainage geocomposites that has been implemented from the previous model and updated with a 3-year test program performed at SAGEOS and USASK laboratories.
- Calculation modules development for drainage geocomposites and granular drainage layers, based on standard design guidance documents from the geosynthetic industry and publications from specialists in these fields.
- User interface design to have a software that is easy to use and intuitive.

The software also offers design firms a company-restricted database allowing multiple users in the same company to share and update their projects.

2.2 User interface

The user interface has been developed to represent the engineer's needs and the design steps as closely as possible. The software is available in several languages (English, French, and Spanish), in SI and US units, and based on ISO and ASTM standards. When creating a new project, the user can choose between several available drainage applications (Figure 1) such as Sub-slab depressurization systems, Drainage behind MSE walls, Cover drainage systems, or Leachate collection systems.

It should be noted that the software allows for the design of drainage geocomposites for both liquid and gas.

Having pre-defined applications makes it easier for the user to be guided through the steps of the design with the required input of specific parameters that are consistent with the application. For example, the input of the water flow to be drained by the drainage geocomposite will be determined from the maximum daily precipitation in the "Cover drainage system" application.

The software also includes calculations to design multi-linear drainage geocomposite as an alternate to a granular drainage layer.

2.3 Database

The Lympha software offers a company restricted database that allows for multiple users in the same company to share their projects (Figure 2). This feature is useful to retrieve a project and update a calculation with new parameters, or to re-generate the report using other units or another language.

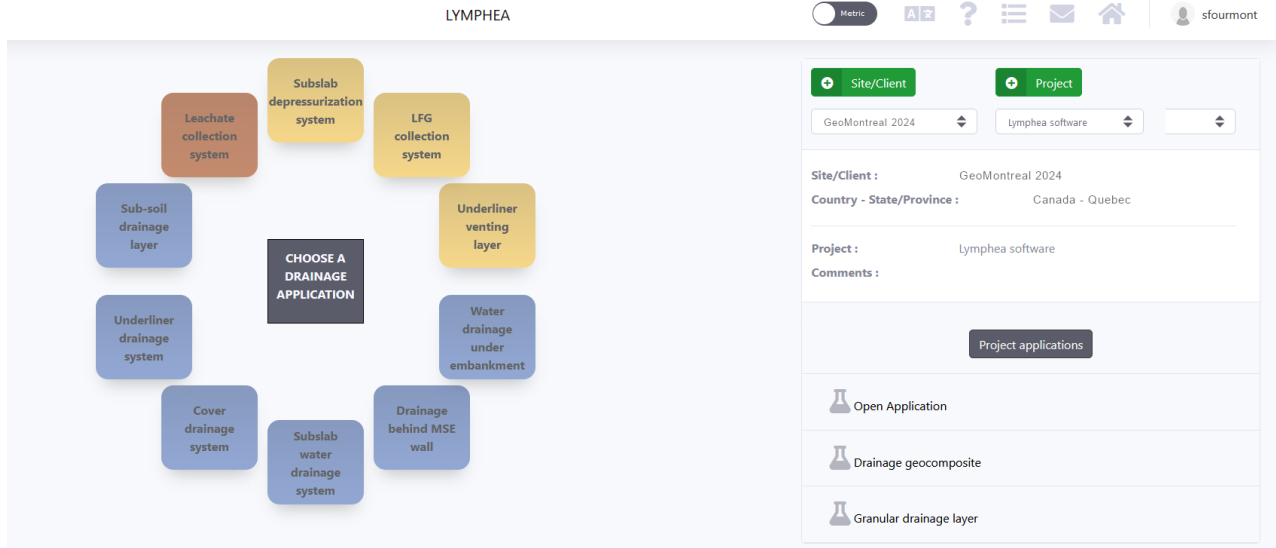


Figure 1. Home page of the software

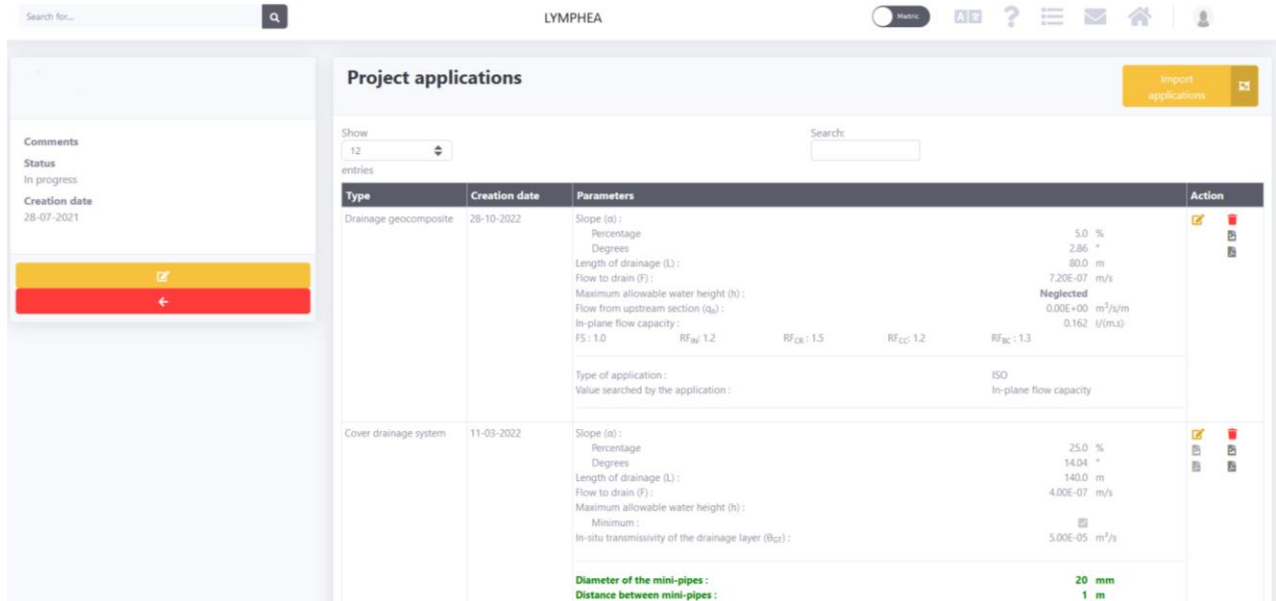


Figure 2. Projects data base

3 CALCULATION MODULE FOR MULTI-LINEAR DRAINAGE GEOCOMPOSITES

The calculation modules for multi-linear drainage geocomposites are based on the previous model initially developed and validated on several large-scale cell experiments 4 m (13 ft) long and 1 m (3 ft) wide at the LIRIGM university research laboratory (Faure et al., 1993), 10 m (33 ft) long and 2 m (6 ft) wide at the Draitube manufacturing site in France (Faure et al., 1994), and confirmed many times since. The theoretical model in the software is based on the following flow conditions:

- Fluid supply with a homogeneous flow distribution perpendicularly to the geocomposite.

- Horizontal or non-horizontal position of the drainage layer with the flow condition down or reverse to the slope α .
- Perforated mini-pipes unsaturated, partially saturated, or fully saturated.

3.1 Hydraulic modelling for water

The liquid inside the drainage layer is assumed to flow perpendicular to the perforated mini-pipes. This hypothesis is conservative and reasonably good as the distance between the mini-pipes is 2 m (6 ft) maximum, provided the length of the mini-pipes is generally more than 10 m (32 ft). The head losses to enter the perforated mini-pipes have been found insignificant compared to the head losses into

the drainage layer. The governing equation of the hydraulic head in the multi-linear drainage geocomposite is then given by Equation 1 from Faure et al. (1993).

$$h_{max} = \frac{F \times D^2}{8\theta_{GT}} + \left(\frac{b}{b+1}\right) \times \left(\frac{F \times D}{a}\right)^{1/b} \times L^{(b+1)/b} - L \times \sin \alpha \quad [1]$$

where F = Flow per unit area; θ_{GT} = Transmissivity of the drainage layer; D = Distance between mini-pipes; L = Length of drainage; a and b = constants experimentally determined from the flow capacity of the mini-pipes.

3.1.1 Flow capacity of the drainage layer

The drainage layer is composed of a non-woven needle-punched staple fibre geotextile. It is protected from the surrounding soil by an additional filter layer, also included as part of the multi-linear drainage geocomposite, that prevents soil particle migration. The flow carried out by the drainage layer is given by Darcy's law and is dependent on its Transmissivity.

Laboratory tests have been performed at SAGEOS and USASK laboratories on several drainage layers under multiple loads to characterize their hydraulic Transmissivity. The transmissivity values considered in the software are in-situ Transmissivity, meaning that reduction factors have already been applied to reflect the long-term drainage capacity under load, in the soil. Recommended reduction factors for geotextile drainage layers are given in the GRI White paper 4. Figure 3 shows an example of the long-term in-situ Transmissivity of a 200 g/m² (6 Oz/sy) drainage layer function of the vertical load applied.

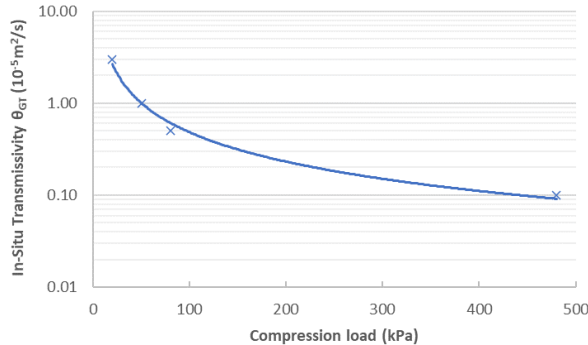


Figure 3. In-Situ Transmissivity of a 200 g/m² non-woven needle punched geotextile drainage layer

3.1.2 Flow capacity of the mini-pipes

Tests have been carried out at SAGEOS laboratory to characterize the flow capacity of the mini-pipes themselves and to confirm the experimental values previously obtained during the development and validation of the software. The flow capacity of the mini-pipes is a function of the hydraulic gradient and has been measured for the 3 mini-pipe diameters: 16 mm (5/8 in), 20 mm (4/5 in), and 25 mm (1 in) as shown in Figure 4. Mini-pipe lengths of 0.5 to 1 m (20 to 40 in) were tested, and the resulting flow capacity was calculated, excluding entrance and exit head pressure losses.

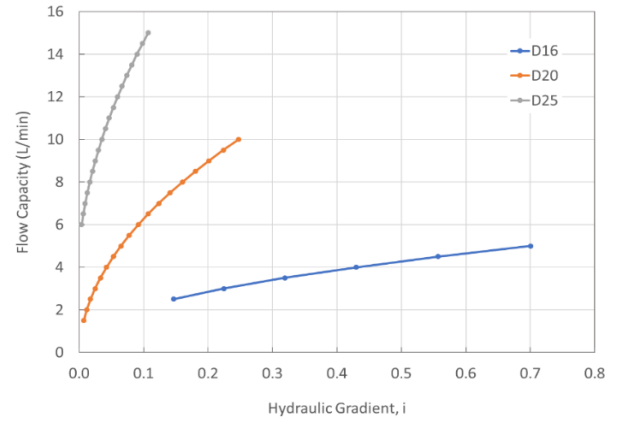


Figure 4. Flow capacity of the 3 mini-pipe diameters

For each mini-pipe diameter, the flow capacity implemented in the software is conservative compared to the test results. A factor of safety of 1.55 has been applied to the measured flow capacity values.

The flow of a fluid in a drain is evaluated using the two non-dimensional parameters, Reynolds number (Re) and head loss coefficient (λ) as per Equations 2 & 3.

$$Re = \frac{Q \times d}{A \times \nu} \quad [2]$$

$$\lambda = \frac{2 \times g \times i}{(Q/A)^2} \quad [3]$$

where Re = Reynolds number, Q = Fluid flow (gas: Q_g , water: Q_w), A = Area, d = Hydraulic diameter of the pipe, ν = Fluid kinematic viscosity (gas: ν_g , water: ν_w), λ = Head loss coefficient, i = Hydraulic gradient (gas: i_g , water: i_w) and g = Gravity.

The gas flow capacity is modeled by considering that for the same Reynolds number, the head loss coefficient remains the same in the drainage geotextile layer and in the mini-pipes. This approach has been found conservative since it gives drained flow rates lower than those actually measured on the mini-pipes with a length up to 100 m (320 ft). The $\frac{Q_g}{Q_w}$ ratio is in fact dependant on the characteristics of the mini-pipes (diameter and roughness) and decreases when the mini-pipe diameter increases (Bannour, 2024).

3.2.1 Flow capacity of the drainage layer

As per the previous statements, we obtain the gas transmissivity of the geotextile drainage layer function of its water transmissivity (Equation 4).

$$\theta_{GT_g} = \frac{\theta_{GT} \times \nu_w}{\nu_g} \quad [4]$$

where θ_{GT} = Water transmissivity of the geotextile drainage layer, θ_{GTg} = Gas transmissivity of the geotextile drainage layer.

3.2.2 Flow capacity of the mini-pipes

The flow in the mini-pipes is turbulent, even for small hydraulic gradients. Then, considering that for the same Reynolds number, the head loss coefficient remains the same, the gas flow capacity of the mini-pipes can be calculated using the Equation 5.

$$Q_{Pg} = a \times i_g^b \quad [5]$$

where Q_{Pg} = Gas flow capacity of the mini-pipes, i_g = Gas hydraulic gradient

4 CALCULATION MODULE FOR GEOCOMPOSITES

The calculation module for drainage geocomposite is based on Darcy's law and the in-plane drainage capacity from ASTM or ISO standard tests.

The hydraulic behavior of the drainage geocomposite is modelled using Equation 6 in an ISO environment and Equation 7 in an ASTM environment. A potential incoming upstream flow has also been taken into account.

$$q_p(\sigma, i, 100h) = FS \times \prod RF \times (F \times L + q_0) \quad [6]$$

$$\theta_{100}(\sigma, i, 100h) = FS \times \prod RF \times \frac{(F \times L + q_0)}{\sin \alpha + \frac{\cos \alpha \times h_{max}}{L}} \quad [7]$$

where $q_p(\sigma, i, 100h)$ = In-plane flow capacity as per ISO 12958-2 (performance test) performed under a vertical load σ , a hydraulic gradient i , and a seating time of 100 hours with boundary conditions representative from the applications; $\theta_{100}(\sigma, i, 100h)$ = Transmissivity as per ASTM D4716 (or GRI GC15) performed under a vertical load σ , a hydraulic gradient i , and a seating time of 100 hours with boundary conditions representative from the applications; FS = Factor of safety; $\prod RF$ = Reduction Factors.

$\prod RF$ is the product of the following reductions factors (Equation 8).

$$\prod RF = RF_{IN} \times RF_{CR} \times RF_{CC} \times RF_{BC} \quad [8]$$

where RF_{IN} = Reduction factor for geotextile intrusion into the drainage core; RF_{CR} = Reduction factor for creep in compression; RF_{CC} = Reduction factor for chemical clogging; RF_{BC} = Reduction factor for Bacteriological clogging.

The reduction factors are dependent on the type of application and are also product/technology specific. Recommended values for the reduction factors are given in the software and are generally taken from the ISO/TR 18228-4 standard guide. It is important to note that the reduction factors are to be applied on $q_p(\sigma, i, 100h)$ or

$\theta_{100}(\sigma, i, 100h)$ i.e. on the 100 hours seating time test results.

Each parameter mentioned in Equations 6 & 7 can be chosen in the software as the value to be determined (as the unknown of the equation).

5 CALCULATION MODULE FOR GRANULAR DRAINAGE LAYER

The calculation module for the granular drainage layer is based on two technical papers published by Giroud et al. in 2000. The approach used is to verify that the maximum water flow height is less than the thickness of the granular drainage layer, which becomes the maximum allowable water height. According to Giroud et al. (2000), the thickness of the liquid layer is influenced by the hydraulic conductivity of the granular layer, the angle of the slope, the drainage length, and the flow rate per unit area entering through the surface perpendicular to the flow direction.

The modeling of the hydraulic behavior of the granular drainage layer is performed using Giroud's formula, where an incoming upstream flow has also been considered, as shown in Equation 9.

$$F \times L + q_0 = K \times \left(h_{max} \times \sin \alpha + \frac{h_{max}^2 \times \cos \alpha}{L} \right) \quad [9]$$

where F = Flow rate per unit area; L = Length of drainage; q_0 = Incoming upstream flow; K = Hydraulic conductivity of the granular layer; h_{max} = Maximum height of water; and α = Slope.

As per the calculation module for drainage geocomposites, the user can solve for each parameter mentioned above as the value to be implemented (as the unknown of the equation) in the software. It allows the user to design a drainage solution with a granular layer function of the input data specific to the project.

Reduction factors for chemical clogging (RF_{CC}) and biological clogging (RF_{BC}) can be addressed and applied to the hydraulic conductivity of the granular layer. The factor of safety (FS) is applied to either h_{max} or K , whichever gives the most conservative result.

6 EXAMPLE OF CALCULATION

An example of the selection of a multi-linear drainage geocomposite to replace a granular drainage layer is presented in this paragraph. The input parameters are presented in the Figure 5.

Sub-soil drainage layer

Please fill the entire form

The decimal separator is forced as a dot "."

Slope (α)

Percentage Degrees

3.0 %

Length of drainage (L) m

Maximum allowable water height (h) m Minimum

Flow to drain (F) m/s

Hydraulic equivalency with a granular layer

Hydraulic conductivity of the granular layer (K) m/s

Thickness of the granular layer (e) m

Factor of Safety (FS)

Figure 5. Input parameters implementation

All the multi-linear drainage geocomposites that have a equivalent or better hydraulic performance than the granular drainage layer will be displayed. The user can select the product and visualize the typical cross section of the project.

In our example, the selected product is composed of mini-pipes 25 mm (1 in) diameter regularly spaced every 0.5 m (20 in) of product width. It drains the flow per unit area of 9.90×10^{-7} m/s (3.25×10^{-6} ft/s), calculated from the granular drainage layer characteristics and the geometry of the project) on a maximum length of drainage of 189 m (620 ft) compared to the 100 m (320 ft) required length. Figure 6 shows the part of the report with the selected multi-linear drainage geocomposite.

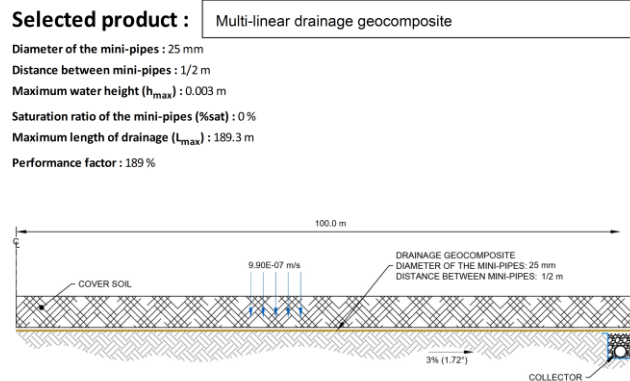


Figure 6. Report with the selected product

7 CONCLUSIONS

The development of a software for the hydraulic design of drainage geocomposite and granular drainage layers is intended to help designers. It is based on formulas and calculation methods well recognized by the geosynthetics drainage industry and it also includes the ability to design multi-linear drainage geocomposites. The Lympha software allows for a wide range of parameters to be determined to better adapt to the site-specific requirements of each project. Considering its usage throughout the world, it also works in both ISO and ASTM environments, using either SI or US units.

Finally, the software is based on a previous model, initially developed, and validated on a large-scale cell experiment and confirmed many times since. The user interface has been designed to be as intuitive as possible, and it guides the user by explaining the important steps and input data to be considered.

8 REFERENCES

- ASTM D4439. Standard Terminology for Geosynthetics, *ASTM International*, West Conshohocken, Pennsylvania, USA.
- ASTM D4716. Standard Test Method for Determining the (In-plane) Flow Rate per Unit Width and Hydraulic Transmissivity of a Geosynthetic Using a Constant Head, *ASTM International*, West Conshohocken, Pennsylvania, USA.
- ASTM D7931. Standard Guide for Specifying Drainage Geocomposites. *ASTM International*, West Conshohocken, Pennsylvania, USA.
- Blond, E., Saunier, P., Daqoune, T. & Fourmont, S. 2013. Assessment of the Effect of Specimens Dimensions on the Measured Transmissivity of Planar Tubular Drainage Geocomposites, *GeoMontreal 2013*, Montreal, Quebec, Canada.
- Blond, E., Saunier, P. & Ragen, W. 2010. Assessment of the resistance of drain tube planar drainage geocomposites to high compressive loads, *9th International Conference on Geosynthetics, Vol. 3*, Guarujá, Brazil.
- Faure Y.H., Matichard Y., Brochier P. & Suryolelono, K. 1993. Experimental and theoretical methodology to validate new geocomposite structures for drainage, *Geotextiles and Geomembranes 12*. 397-412.
- Giroud, J.P., Zornberg, J.G., & Zhao, A. 2000. Hydraulic design of geosynthetic and granular liquid collection layers, *Geosynthetics International, Special Issue on Liquid Collection Systems, Vol. 7*. 285-380.
- Giroud, J.P., Zornberg, J.G. & Beech, J.F. 2000. Hydraulic design of geosynthetic and granular liquid collection layers comprising two different slopes, *Geosynthetics International, Special Issue on Liquid Collection Systems, Vol. 7*. 453-489.
- GRI GC15. 2017. Standard Test Method for Determining the Flow Rate per Unit Width of Drainage Geocomposites with Discrete High Flow Components, *Geosynthetic Institute*, Folsom, Pennsylvania, USA.

- GRI White paper 4. 2007. Reduction Factors (RFs) used in geosynthetic design, *Geosynthetic Institute*, Folsom, Pennsylvania, USA.
- ISO 12958-2. Geotextiles and geotextile-related products - Determination of water flow capacity in their plane - Part 2: Performance test, *International Organization for Standardization*, Geneva, Switzerland.
- ISO/TR 18228-4. Design using geosynthetics - Part 4: Drainage, *International Organization for Standardization*, Geneva, Switzerland.
- Zanzinger, H. 2000. Reduction factors for the long-term water flow capacity of drainage geocomposites, *3rd international conference Geofilters 2000*, Warsaw, Poland.
- Zhao, A. & Montanelli, F. 1999. Effect of soil presence on flow capacity of drainage geocomposites under high normal loads, *Geosynthetics 1999 conference*, Boston, Massachusetts, USA.